

## Barium and Strontium Cobaltites, Synthesized in A Solar Furnace

MS Paizullakhanov<sup>1\*</sup>, OT Rajamatov<sup>2</sup>, AA Holmatov<sup>2</sup>, NH Karshieva<sup>3</sup>

<sup>1</sup>Material sciences institute

<sup>2</sup>Fergana politechnik institute

<sup>3</sup>Tashkent stat technical university

**\*Corresponding author:** MS Paizullakhanov, Material sciences institute, Material sciences institute Uzbekistan, Tel: +998942131243, E-mail: fayz@bk.ru

**Citation:** MS Paizullakhanov, OT Rajamatov, AA Holmatov, NH Karshieva (2022) Barium and Strontium Cobaltites, Synthesized in A Solar Furnace. Int J Nucl Mater 1: 1-5

**Copyright:** © 2022 MS Paizullakhanov. This is an open-access article distributed under the terms of Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

### ABSTRACT

In general, nanotechnology can be understood as a technology of design, fabrication and applications of nanostructures and nanomaterials, as well as fundamental understanding of physical properties and phenomena of nanomaterials and nanostructures. In recent years development of industries like textile, leather, paint, food, plastics, and cosmetics is enlarged and these industries are connected with the discarding of a vast number of organic pollutants which are harmful to microbes, aquatic system, and human health by influencing the different parameters. So the fabrication of those nanomaterials (coupled or doped) to form heterojunctions provides an effective way to better harvest solar energy and to facilitate charge separation and transfer, thus enhancing the photocatalytic activity and stability. We expect this review to provide a guideline for readers to gain a clear picture of fabrication and application of different type heterostructured photocatalysts. In this review, starting from the photocatalytic reaction mechanism and the preparation of the photocatalyst, we review the classification of current photocatalysts, preparation methods, factor that affect photocatalytic reaction, characterization of photocatalysts and the methods for improving photocatalytic performance. This review also aims to provide basic and comprehensive information on the industrialization of photocatalysis technology.

**Keywords:** Nanotechnology; Heterostructure; Photocatalyst; Doping; Coupling; Photocatalysis

## Introduction

It is known that perovskite cobaltites of strontium  $\text{SrCoO}_{3-\delta}$  and barium  $\text{BaCoO}_3$  exhibit a wide range of electronic and magnetic characteristics and are of great interest. A feature of such compounds is the possibility of influencing their transport properties by varying the concentration of anionic vacancies [1]. At the same time, synthesis at high pressures makes it possible to obtain an ideal oxygen stoichiometry ( $\delta=0$ ). For example,  $\text{SrCoO}_3$  obtained at 6 GPa [2, 3] is a simple cubic perovskite structure.

When  $\text{SrCoO}_{3-\delta}$  oxides are produced at ambient pressure in air, they exhibit the approximate stoichiometry of  $\text{Sr}_2\text{Co}_2\text{O}_5$  (or  $\text{SrCoO}_{2.5}$ ). The observed high-temperature brownmillerite-like structures, the so-called “high-temperature phases”, and the hexagonal structures, called “low-temperature phases” are stabilized due to order-disorder transitions of oxygen vacancies. The complete ordering of vacancies with the formation of the brownmillerite phase is established within a few seconds during quenching after high-temperature (usually 1000°C) solid-phase synthesis [1, 4, 5].

Recently, more and more attention has been paid to barium cobaltite oxide due to its semiconductor characteristics [6-9]. Materials based on  $\text{BaCoO}_{3-\delta}$  doped with some other elements have low resistivity at low temperatures and can be used as thermistors.

In this work, we studied perovskite structures based on barium and strontium cobaltites obtained by melt synthesis in a solar furnace of the corresponding mixture of barium and/or strontium carbonates with cobalt oxide:  $\text{BCO}_3 + \text{Co}_2\text{O}_3$ ;  $\text{SrCO}_3$ . From the mixture after grinding (63  $\mu\text{m}$ ) and molding by semi-dry pressing ( $P = 1\text{t}$ ), samples were made in the form of a cylinder 20 mm, which were installed on a water-cooled melting unit located on the focal plane of the solar furnace. A concentrated flux of solar radiation with a density of the order of  $Q=150\text{ W/cm}^2$  was directed to the sample. Such a value of the flux density according to the law of Stefan Boltzmann  $\tau = \sqrt[4]{\frac{Q}{\sigma}}$ , where  $\sigma=5.67 \times 10^{-8}\text{ W/m}^2\text{K}$  is the Stefan Boltzmann constant, corresponded to the temperature of the heated body of 1900°C. At this temperature, the sample melted. Melt droplets fell into water and cooled at a rate of  $10^3\text{ deg/s}$ .

Such cooling conditions made it possible to fix the high-temperature structural states of the material.


Drops of the melt, loaded into the water, cracked into small glass-like particles of arbitrary shape. To study such a material, it was ground to a fineness of 60  $\mu\text{m}$ , dried at 400°C, and samples were molded in the form of cylinders  $\varnothing 8\text{mm}$  15mm high for firing at a temperature of 1000°C followed by arbitrary cooling.

The obtained samples were subjected to X-ray phase analysis using a DRON-3M installation with a copper anode with K- $\alpha$  radiation in the Bragg-Brentano reflection geometry with  $\text{CuK}\alpha$  radiation ( $\lambda = 1.5418\text{ \AA}$ ). The data were obtained between  $20 \leq 2\theta \leq 60^\circ$ .

The slit system was chosen to ensure that the X-ray beam was completely within the sample over the entire  $2\theta$  range.

The temperature coefficient of thermal expansion was measured on a cathetometer in the temperature range 25 - 950°C. The electrical resistance was measured by the four-contact method in the temperature range 25 - 1000°C.

The density of the samples was determined pycnometrically  $\rho_{ef} = \frac{m}{V_{ef}}$ , the value of which was  $4.87\text{ g/cm}^3$  for  $\text{BaCoO}_3$  and  $4.64\text{ g/cm}^3$  for  $\text{SrCoO}_3$ .

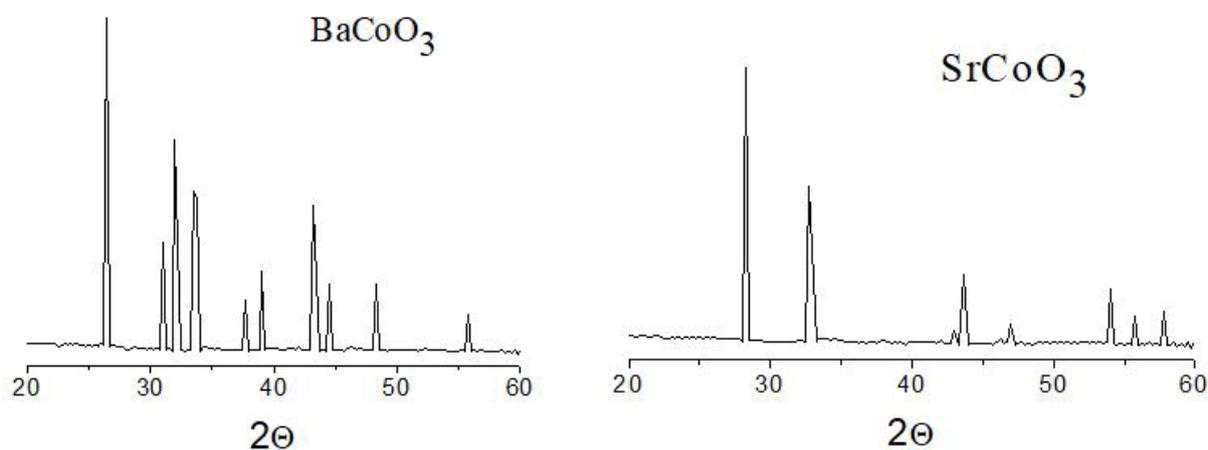

**Figure 1:** shows X-ray patterns of barium and strontium perovskite cobaltites.


Fig.1. X-ray patterns of perovskite structures of a) barium cobaltites  $\text{BaCoO}_3$  and b) strontium  $\text{SrCoO}_3$  obtained from a melt in a solar furnace

The analysis of X-ray patterns showed that for the case of  $\text{BaCoO}_3$  the diffraction pattern is described by a hexagonal lattice of space group  $P63/mmc$  with lattice parameters  $a=5.652 \text{ \AA}$ ,  $c=4.763 \text{ \AA}$ . In the case of strontium cobaltite  $\text{SrCoO}_3$ , a hexagonal structure is also observed with lattice parameters  $a=9.511 \text{ \AA}$ ,  $c=12.287 \text{ \AA}$ .


Figure 2 shows SEM micrographs of barium and strontium cobaltites obtained by melt quenching in a solar furnace.

SEM analysis of  $\text{BaCoO}_{3-\delta}$  micrographs shows that the grains have a fine and uniform microstructure. The average ceramic grain size is  $3 \mu\text{m}$ . The relative density of the samples was 94%. The dense microstructure made it possible to obtain good reproducibility of the electrical characteristics of the ceramics.

The temperature coefficient of thermal expansion of the samples in the temperature range 25 - 950°C was  $\alpha = 11.7 \times 10^{-6} \text{ K}^{-1}$  for  $\text{SrCoO}_3$  and  $\alpha = 14.1 \times 10^{-6} \text{ K}^{-1}$  for  $\text{BaCoO}_3$

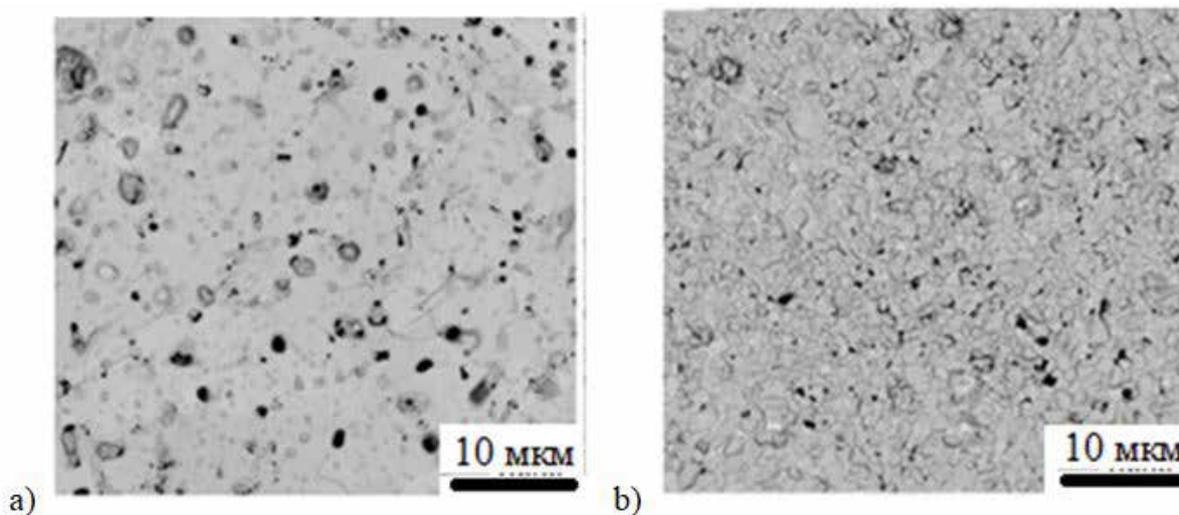

**Figure 2:** SEM micrographs of barium (a) and strontium (b) cobaltites obtained by melt quenching in a solar furnace. The temperature dependence of resistivity ( $\rho$ ) and samples are shown in Fig.3.

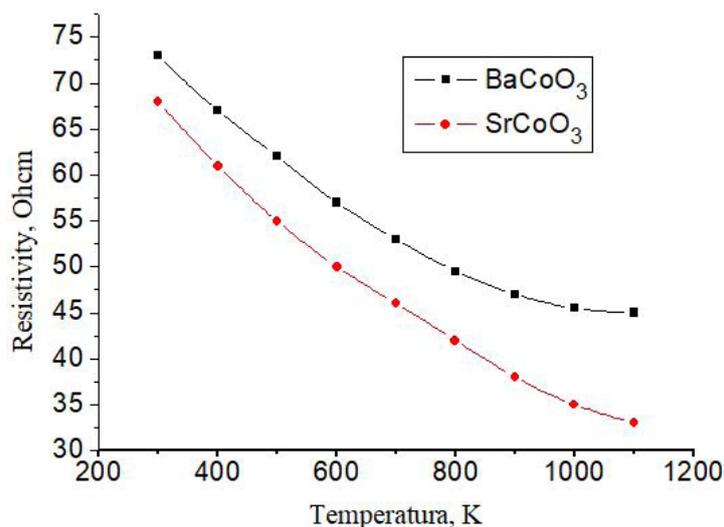

**Figure 3:** Temperature dependences of the electrical resistance of barium and strontium cobaltites in the temperature range 300 - 1200K

As can be seen from Fig. 3, the resistivity decreases exponentially with increasing temperature. Resistivity depends on temperature and can be expressed by the Arrhenius equation

$$\rho = \rho_0 \exp\left(-\frac{E_a}{kT}\right)$$

where  $\rho$  and  $\rho_0$  are electrical resistivity at a certain temperature and room temperature, respectively.  $E_a$  is the activation energy of electrical conductivity. The analysis of the obtained results made it possible to determine the activation energy equal to 0.01 eV. The obtained results indicate that BaCoO<sub>3</sub> and CaCoO<sub>3</sub> cobaltites, demonstrating high electrical conductivity and low thermal expansion coefficient, can be used as a promising thermoelectric material [10].

Thus, the technological route, which includes melting a stoichiometric mixture of cobalt oxide with barium or strontium carbonates in a solar furnace, quenching the melt into water, grinding the casting and molding, followed by sintering at 11000C, makes it possible to obtain a material based on hexagonal barium and strontium cobaltites with a developed fine microstructure and semiconductor nature of the electrical conductivity. The materials, exhibiting high values of electrical conductivity and low coefficient of thermal expansion, can be used as a promising thermoelectric material.

## References

1. JG Grenier, S Ghodbane, G Demazeau, M Pouchard, P Hagenmuller, et al. (1979) ChemInform Abstract: Synthesis, Structural, Magnetic, and Electrical Study of  $\text{BaSrCo}_2\text{O}_5$ , a Highly Disordered Cubic Perovskite Mat Res Bull, 14,831.
2. XL Wang, H Sakurai, E Takayama-Muromachi (2003) Synthesis, structures, and magnetic properties of novel Ruddlesden–Popper homologous series  $\text{Sr}_{n+1}\text{Co}_n\text{O}_{3n+1}$  ( $n=1,2,3,4$ , and  $\infty$ ) J Appl Phys, 97: 10M519.
3. Z Q Deng, W S Yang, W Liu, C S Chen (2006) Oxygen-Vacancy-Related Structural Phase Transition of  $\text{Ba}_{0.8}\text{Sr}_{0.2}\text{Co}_{0.8}\text{Fe}_{0.2}\text{O}_{3-\delta}$  J Solid State Chem 179:362.
4. H Watanabe, T Takeda (1970) Proc Int Conf on Ferrites, Japan 598.
5. Wei Zhou, Ran Ran (2009) Wanqin Jin In situ templating synthesis of conic  $\text{Ba}_{0.5}\text{Sr}_{0.5}\text{Co}_{0.8}\text{Fe}_{0.2}\text{O}_{3-\delta}$  perovskite at elevated temperature Bulletin of Materials Science.
6. JC Yao, JH Wang, Q Zhao, AM Chang (2013) Int J Appl Ceram Technol 10, E106.
7. Zhenhua Hu, Huimin Zhang, Junhua Wang (2017) Fabrication and thermosensitive characteristics of  $\text{BaCoO}_{3-\delta}$  ceramics for low temperature negative temperature coefficient thermistor. Journal of Materials Science: Materials in Electronics 28.
8. K Yamaura, HW Zandbergen, K Abe, RJ Cava, (1999) “Synthesis and Properties of the Structurally One-Dimensional Cobalt Oxide  $\text{Ba}_{1-x}\text{Sr}_x\text{CoO}_{3-d}$ ”, J Sol St Chem **146**:96 .
9. C Felser, K Yamaura, RJ Cava (1999) “The Electronic Band Structure of  $\text{BaCoO}_3$ ,” J Sol St Chem 146:411.
10. Oxide (2002) Thermoelectrics Research Signpost / ed by K Koumoto, I Terasaki, N Murayama – India: Trivandrum, – 255.